



# Osteogenic Differentiation and Proliferation of Apical Papilla Stem Cells Using Chitosan-Coated Nanohydroxyapatite and Bioactive Glass Nanoparticles

Sara Elshahat<sup>1</sup> Abeer Abdelhakim Elgendy<sup>1</sup> Tarek Elsewify<sup>1,2</sup> 

<sup>1</sup>Endodontic Department, Faculty of Dentistry, Ain Shams University, Cairo, Egypt

<sup>2</sup>Restorative Dental Sciences Department, College of Dentistry, Gulf Medical University, Ajman, UAE

**Address for correspondence** Tarek Medhat Elsewify, Department of Endodontics, Faculty of Dentistry, Ain Shams University, Cairo, Egypt Restorative Dental Sciences Department, College of Dentistry, Gulf Medical University, Ajman, UAE (e-mail: tarek\_elsewify@dent.asu.edu.eg; dr.tarek@gmu.ac.ae).

Eur J Dent

## Abstract

**Objective** The aim of this study was to evaluate the osteogenic differentiation ability and proliferation of apical papilla stem cells (SCAPs) using chitosan-coated nanohydroxyapatite and bioactive glass nanoparticles.

**Materials and Methods** Hydroxyapatite, chitosan-coated nanohydroxyapatite, and bioactive glass 45S5 nanoparticles were prepared and characterized using a transmission electron microscope and X-ray diffraction. SCAPs were harvested from freshly extracted impacted wisdom teeth, cultured, and characterized using flow cytometric analysis. Tested nanomaterials were mixed and samples were classified into five equal groups as follows: negative control group: SCAP with Dulbecco's modified eagle's medium, positive control group: SCAP with inductive media, first experimental group: nanohydroxyapatite with SCAP, second experimental group: chitosan-coated nanohydroxyapatite with SCAP, third experimental group: bioactive glass nanoparticles with SCAP. Osteoblastic differentiation was assessed using an alkaline phosphatase (ALP) assay. Receptor activator of nuclear factor kappa beta ligand (RANKL) expression was evaluated using specific polyclonal antibodies by fluorescence microscope. The proliferation of SCAP was assessed using cell count and viability of trypan blue in addition to an 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) assay.

**Results** Isolated SCAP showed a nonhematopoietic origin. Chitosan-coated nanohydroxyapatite showed the highest ALP concentration followed by nanobioactive glass, nanohydroxyapatite, and negative control. Chitosan-coated nanohydroxyapatite showed the highest H score followed by nanobioactive glass, nanohydroxyapatite, and negative control in RANKL expression. Chitosan-coated nanohydroxyapatite showed the highest viable cell count.

**Conclusion** SCAP isolation is achievable from extracted fully impacted immature third molars. All tested biomaterials have the ability to induce osteogenic differentiation and proliferation of SCAP. Composite nanoparticle materials show better osteogenic differentiation and proliferation of SCAP than single nanoparticles.

## Keywords

- ▶ osteoinduction
- ▶ osteoconduction
- ▶ regenerative endodontic

DOI <https://doi.org/10.1055/s-0043-1777044>.  
ISSN 1305-7456.

© 2024. The Author(s).

This is an open access article published by Thieme under the terms of the Creative Commons Attribution License, permitting unrestricted use, distribution, and reproduction so long as the original work is properly cited. (<https://creativecommons.org/licenses/by/4.0/>)

Thieme Medical and Scientific Publishers Pvt. Ltd., A-12, 2nd Floor, Sector 2, Noida-201301 UP, India

## Introduction

Regenerative endodontic procedures are considered nowadays the ideal treatment for necrotic immature permanent teeth. These procedures will allow for hard tissue formation completing the root structure in length and thickness. Stem cells, growth factors, and scaffolds are the three major components of regenerative endodontic procedures.<sup>1</sup>

Dental pulp stem cells, stem cells from human exfoliated deciduous teeth, periodontal ligament stem cells, and stem cells of the apical papilla can now be isolated. Apical papilla stem cells (SCAPs) are located at the apical part of immature teeth.<sup>2</sup> Osteogenic differentiation of SCAPs and the formation of osteoblast and osteoblast-like cells have been demonstrated in addition to the formation of new hard tissue.<sup>3</sup>

Bioactive glass (BG) has been successfully used with implant placement and to treat pathological periodontal bony defects owing to its superior biocompatibility, osteoconductive and -inductive properties. BG has the ability to modify osteoblastic gene expression in a way that properly controls cell proliferation and differentiation.<sup>4,5</sup> Applying the BG in a nano-sized particles, 45S5 BG, has increased its osteoconduction, osteoinduction properties and allowed for its use in bone tissue engineering.<sup>6,7</sup>

Hydroxyapatite shows excellent biocompatibility. Preparing it in the nanoscale yielded superior biologic properties when used as a scaffold owing to particle size similar to that of the natural hydroxyapatite. Nanohydroxyapatite has yielded promising results in various regenerative procedures and led to the creation of various composite scaffolds.<sup>8</sup>

Chitosan, extracted from crustaceans, has been recently used and tested in various endodontic applications owing to its excellent biologic behavior. It is a cationic polymer that demonstrates good antimicrobial properties.<sup>9–11</sup> Composite scaffolds such as chitosan/hydroxyapatite have shown promising osteoconductivity, gaining the advantage of both materials used.<sup>12</sup>

The effect of hydroxyapatite coated by chitosan nanoparticles and BG nanoparticles on the osteogenic differentiation and proliferation of stem cells of the apical papilla has not yet been evaluated. Therefore, the aim of this study was to evaluate the effect of hydroxyapatite coated by chitosan nanoparticles and BG nanoparticles on the osteogenic differentiation and proliferation ability of stem cells of the apical papilla. The null hypothesis tested is that there is no significant difference between the hydroxyapatite coated by chitosan nanoparticles and BG nanoparticles on the osteogenic differentiation and proliferation of stem cells of the apical papilla.

## Materials and Methods

### Preparation of Nanomaterials

#### Bioactive Glass 45S5 Nanoparticles

The sol-gel method was adopted to prepare BG 45S5 nanoparticles from a colloidal solution of 45S5 composition (45 mol% SiO<sub>2</sub>, 24.5 mol% CaO, 24.5 mol% Na<sub>2</sub>O and 6 mol%

P<sub>2</sub>O<sub>5</sub>).<sup>13</sup> Ceramic powder was produced from the gel after heating.

#### Hydroxyapatite Nanoparticles

Ammonium hydroxide and calcium nitrate were used to synthesize the hydroxyapatite nanoparticles following the methodology previously described by Cengiz et al.<sup>14</sup>

#### Chitosan-Coated Nanohydroxyapatite

Preparation of the composite chitosan-coated nanohydroxyapatite was done following Nikpour et al methodology.<sup>15</sup> Powder was obtained after freeze-drying of the mixture.

Characterization of all of the prepared nanoparticles was done using high-resolution transmission electron microscopy (TEM) and X-ray Powder Diffraction (XRD) with 2 theta (10°-70°), with a scanning speed of 1°/min and minimum step size 2Theta: 0.001 at wavelength (K $\alpha$ ) = 1.54614<sup>16</sup> as shown in ►Fig. 1.

#### Stem Cells Harvesting and Culture

SCAPs were harvested and cultured from freshly extracted wisdom teeth of three patients after obtaining an informed consent. Inverted phase contrast microscope was used to check for growth and/or contamination.<sup>17</sup>

#### SCAP Characterization

Flow cytometric analysis was performed using the protocol published earlier on Navios software.<sup>17</sup>

#### SCAP Culture


Cells cultured in complete culture media and harvested after the third passage. The harvested SCAPs were cryopreserved at °80°C for further analysis.<sup>17</sup>

All tested nanomaterials were mixed according to manufacturer instructions. The samples were classified to five equal groups:

- **Negative control group:** SCAP with Dulbecco's Modified Eagle Medium (DMEM).
- **Positive control group:** SCAP with inductive media (OM).
- **Group I:** Nanohydroxyapatite (NHAP 10 µg/mL) with SCAP.
- **Group II:** Chitosan-coated nanohydroxyapatite (NHAP/chitosan 10 µg/mL) with SCAP.
- **Group III:** BG nanoparticles (NBG 500 µg/mL) with SCAP.

For osteoblastic differentiation, six-well plates were used to culture stem cells of the apical papilla OM seeded at 4.5 × 10<sup>5</sup> cells/well. Plates were incubated for a period of 72 hours at 37°C and 5% CO<sub>2</sub>. The activity of alkaline phosphatase (ALP) was measured using enzymatic dephosphorylation by ALP assay kit. For testing the expression of RANKL for SCAP, the cells were examined using specific polyclonal antibody by fluorescence microscope.

Regarding evaluation of the proliferation, the SCAPs were stained by trypan blue and counted by hemocytometer to estimate the number of dead cells. The MTT assay was performed using the Vybrant MTT Cell Proliferation Assay Kit. Cell viability was determined by measuring the optical density at 570 nm on a spectrophotometer.

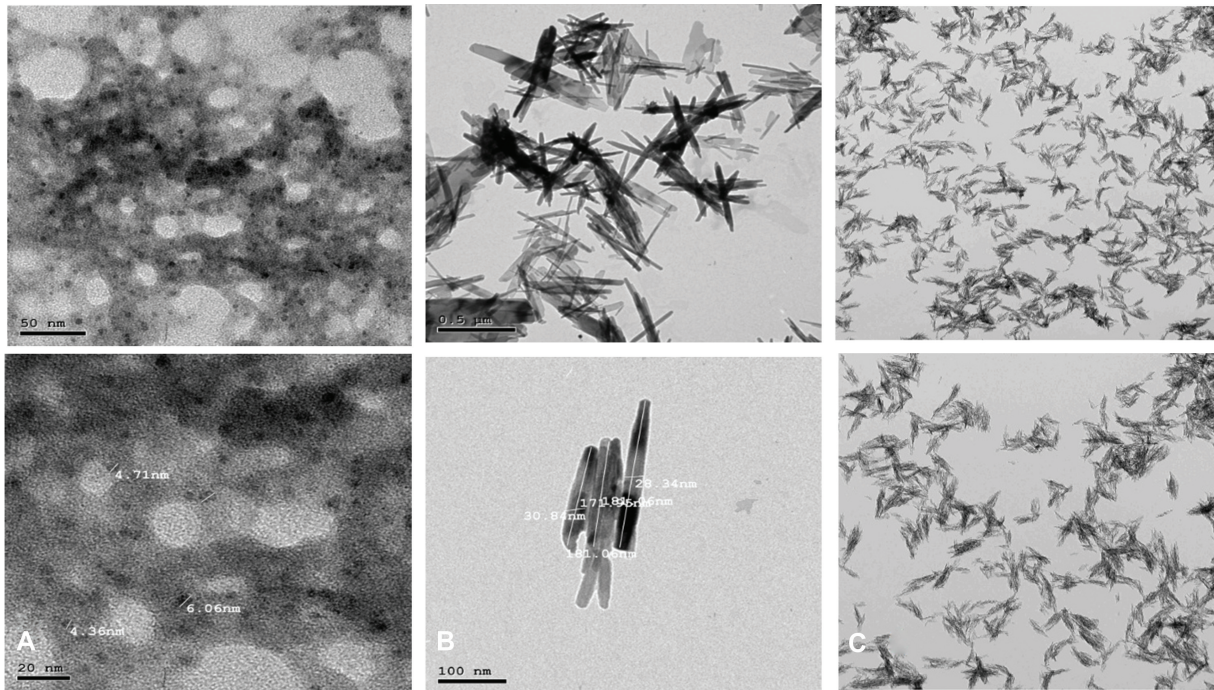

**Fig. 1** Transmission electron microscopic image of (A) bioactive glass 45S5 nanoparticles, (B) hydroxyapatite nanoparticles, and (C) chitosan-coated nanohydroxyapatite nanoparticles.

### Statistical Analysis

Mean and standard deviation values of each group were calculated. Shapiro–Wilk test and Levene’s test were used to test for normality of the data. One-way analysis of variance test was run followed by Tukey’s post hoc test as the data was normally distributed. The significance level was set at *p*-value less than 0.05. Statistical analysis was performed with Statistical package for Social Science software.

### Results

The observed results of the characterized SCAP revealed that the cells showed double bright surface expression of CD44/CD73 and failed to express CD45, indicating a nonhematopoietic origin as shown in ►Fig. 2.

NHAP/chitosan showed the highest ALP concentration followed by NBG, NHAP, and DMEM-NC as shown in ►Table 1. RANKL expression results are shown in ►Table 2 and ►Fig. 3 where NHAP/chitosan showed the highest H score followed by NBG, NHAP, and DMEM-NC. NHAP/chitosan showed the highest viable cell count as shown in ►Table 3. NHAP/chitosan showed the highest viable count also using the MTT assay, although the difference was not statistically significant as shown in ►Table 4.

### Discussion

Proper management and long-term success of nonvital immature permanent teeth continue to be a challenge for clinicians. The ability to regenerate a pulp or pulp-like structure that can lay down hard tissue structure increasing the root length and thickness will increase the tooth’s

fracture resistance and maintain it in function for a longer duration.<sup>18</sup>


During various regenerative endodontic procedures, mesenchymal stem cells have been demonstrated related to immature teeth in addition to mature ones. The origin of such mesenchymal stem cells is believed to be the apical papilla, bone, Periodontal ligament (PDL), and/or granulomas.<sup>19</sup>

Apical papilla can be defined as the loosely attached soft tissue related to the root end of immature teeth. This apical papilla is separated from the dental pulpal tissue by a cell rich zone. The dental pulpal tissue shows more cellular and vascular elements than does the apical papilla.<sup>2</sup>

SCAPs were first isolated by Sonoyama et al. SCAPs are derived from an embryonic neural crest-like tissue, located at the root end of immature teeth. In contrast to other isolated types of stem cells, SCAPs demonstrate impressive odontogenic differentiation and proliferation in addition to massive dentinogenesis.<sup>2,20</sup>

Under favorable conditions, mineral trioxide aggregates have the ability to stimulate the proliferation and differentiation of SCAPs resulting in hard tissue formation. However, the effect of other materials on SCAPs is not well studied.<sup>21</sup> BG, hydroxyapatite, and chitosan have shown promising results when tested for their biologic effect on dental pulp stem cells and mesenchymal stem cells.<sup>22</sup> The aim of the current study was to investigate the effect of nanohydroxyapatite coated by chitosan and nano-BG on osteogenic differentiation and proliferation of stem cells of the apical papilla.

Trypan blue was used for counting the viable cells in the current study owing to its characteristic ability to stain only the dead cells following penetration of its cell membrane.<sup>28,29</sup> The MTT assay was used due to its capability to

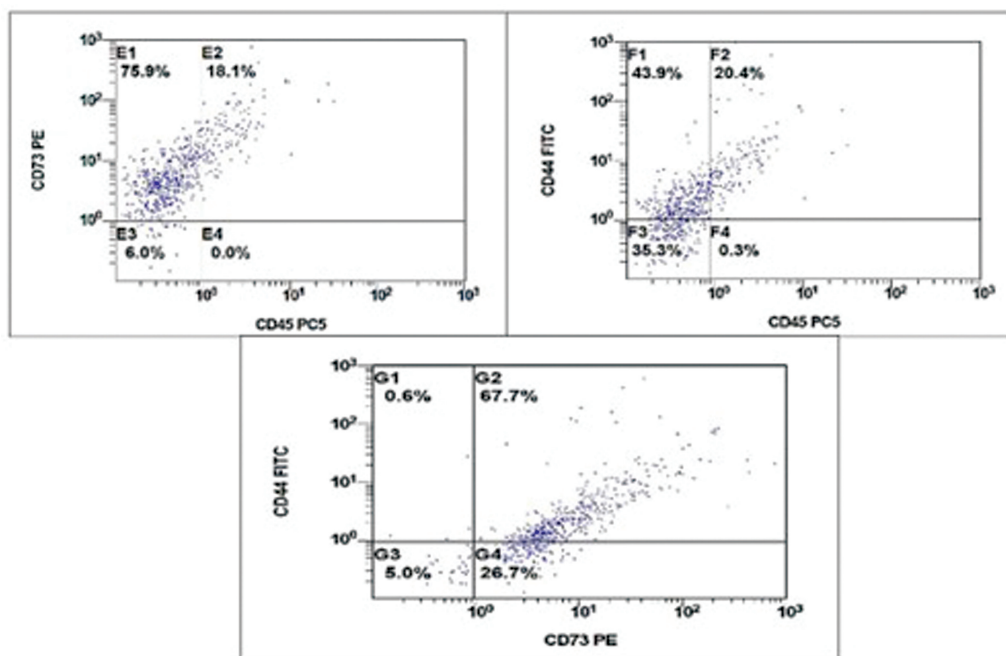

**Fig. 2** Flow cytometry (FCM) dot plots showing the gate protocol for apical papilla stem cells (SCAPs). The SCAPs were stained with stem cell markers (CD73, CD44, and CD45). The CD73 and CD44 positive cells were gated in corresponding to CD45.

**Table 1** Mean  $\pm$  SD and *p*-values of ALP concentration of all tested groups

	(OM-PC)	(NHAP 10 $\mu$ g/mL)	NHAP/chitosan (10 $\mu$ g/mL]	NBG (500 $\mu$ g/mL)	(DMEM-NC)
Mean $\pm$ SD	77.86 $\pm$ 0.15 <sup>b</sup>	68.72 $\pm$ 0.13 <sup>c</sup>	82.90 $\pm$ 0.10 <sup>a</sup>	70.36 $\pm$ 0.10 <sup>d</sup>	55.18 $\pm$ 0.8 <sup>e</sup>
<i>p</i> -Value	<0.001				

Abbreviations: ALP, alkaline phosphatase; NBG, bioactive glass nanoparticles; NHAP, nanohydroxyapatite; SD, standard deviation. Means with different letters were statically significant.

**Table 2** Mean  $\pm$  SD and *p*-values of IF assay of all tested groups

	(OM-PC)	(NHAP 10 $\mu$ g/mL)	NHAP/chitosan (10 $\mu$ g/mL)	NBG (500 $\mu$ g/mL)	(DMEM-NC)
Mean $\pm$ SD	82.67 $\pm$ 1.53 <sup>c</sup>	67.67 $\pm$ 2.52 <sup>d</sup>	180.67 $\pm$ 4.04 <sup>a</sup>	154.67 $\pm$ 4.16 <sup>b</sup>	17.68 $\pm$ 1.52 <sup>e</sup>
<i>p</i> -Value	<0.001				


Abbreviations: IF, immunofluorescence; NBG, bioactive glass nanoparticles; NHAP, nanohydroxyapatite; SD, standard deviation. Means with different letters were statically significant.

determine the mitochondrial activity.<sup>30,31</sup> ALP enzyme activity assays were used as a measure of SCAP differentiation into osteoblast-like cell as it is considered as a characteristic marker for bone-forming cell differentiation.<sup>32</sup> Immunofluorescence assay is considered as one of the most reliable tests that helps elaborate specific protein of interest through antigen-antibody reaction.<sup>33</sup> The RANK-L concentration is proportional to the number of osteogenic cells because it is deemed mandatory for its differentiation.<sup>34,35</sup>

Our results of SCAP characterization come in full agreement with Kang et al who also confirmed the nonhemopoietic origin of the stem cells by lack of CD45 expression.<sup>36</sup>

The superior results of NHAP/chitosan group regarding the ALP and RANKL come in full agreement with Kong et al.<sup>37</sup> This superiority could be attributed to the composite nature of this group that allowed for better mineralization and differentiation. This can be explained by the increased levels of calcium phosphate and calcium carbonate.<sup>38</sup> This also comes in agreement with Ge et al<sup>39</sup> who tested this composite on periodontal ligament stem cells differentiation. They attributed their results to increased concentration of the calcium and phosphate ions.

The NHAP/chitosan group also showed superior results in osteogenic differentiation and proliferation potential of

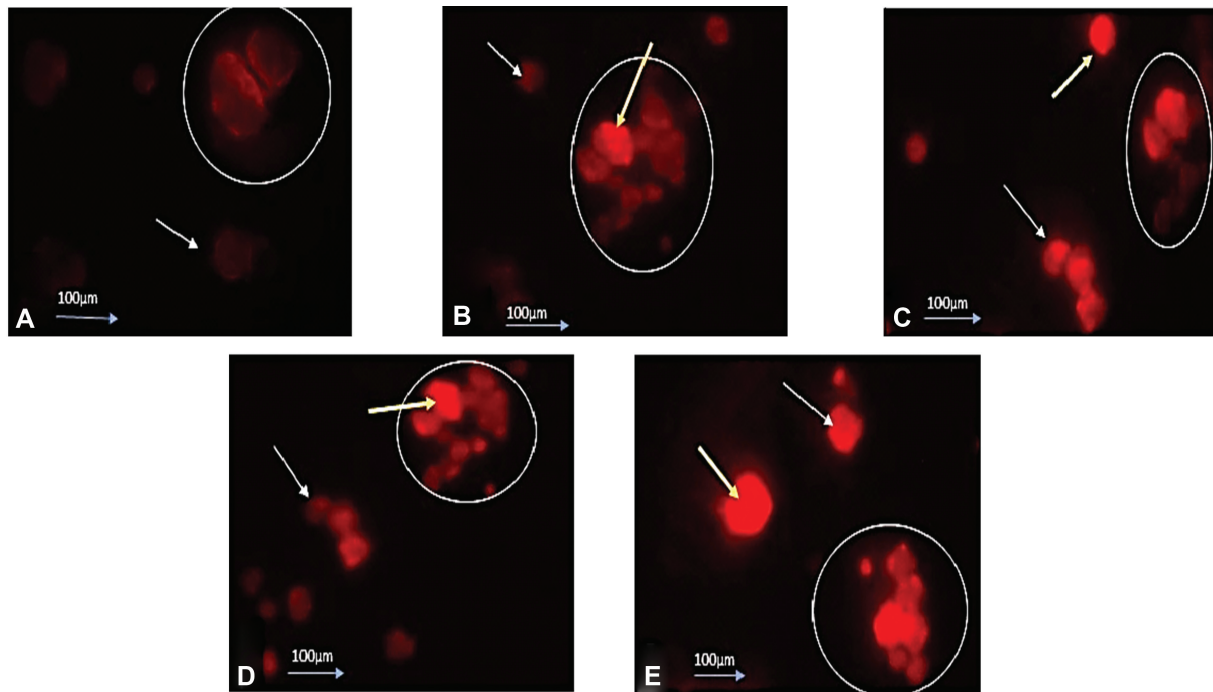

**Fig. 3** Photomicrograph showing expression of RANKL protein in differentiated apical papilla stem cells (SCAPs), the photos were captured by LABOMED Immunofluorescence microscopes. (A) Negative control cells shows small colonies of cells that showed a homogenous faint expression of RANKL, the expression was localized to the cell membrane. (B) Positive control cells with increased number of osteoblasts like colonies which are presented with dense homogenous expression of RANKL. However, the SCAP cultured with nanohydroxyapatite (NHAP) (C), NHAP/chitosan (D) and bioactive glass nanoparticles (E), showed a merged large colony of osteoblast like cells with dense homogenous membranous and nuclear expression of RANKL. The magnification power is 10x. The white circles highlight the osteoblast like colonies, white arrow: membranous expression of RANKL, yellow arrow: dense nuclear expression of RANKL.

**Table 3** Total, dead, viable cell counts, and mean  $\pm$  SD values for tested groups

	Total cell count	Dead cell count	Viable cell count	% Viability
(OM-PC)	$60.7 \times 10^5 \pm 34.2 \times 10^5$ <sup>b</sup>	$7.34 \times 10^3 \pm 1.89 \times 10^3$ <sup>b</sup>	$60.6 \times 10^5 \pm 34.2 \times 10^5$ <sup>b</sup>	99.879
NHAP (10 µg/mL)	$157 \times 10^5 \pm 33.8 \times 10^5$ <sup>a</sup>	$5.28 \times 10^3 \pm 0.88 \times 10^3$ <sup>b</sup>	$157 \times 10^5 \pm 33.8 \times 10^5$ <sup>a</sup>	99.966
NHAP/Ch (10 µg/mL)	$218 \times 10^5 \pm 7.21 \times 10^5$ <sup>b</sup>	$1.64 \times 10^3 \pm 0.12 \times 10^3$ <sup>b</sup>	$218 \times 10^5 \pm 7.21 \times 10^5$ <sup>a</sup>	99.996
NBG (500 µg/mL)	$198.7 \times 10^5 \pm 69.8 \times 10^5$ <sup>a</sup>	$18.9 \times 10^3 \pm 7.80 \times 10^3$ <sup>a</sup>	$198.7 \times 10^5 \pm 69.8 \times 10^5$ <sup>a</sup>	99.905
(DMEM-NC)	$4.647 \times 10^5 \pm 1.147 \times 10^5$ <sup>b</sup>	$4.11 \times 10^3 \pm 4.41 \times 10^3$ <sup>a</sup>	$4.6 \times 10^5 \pm 1.1 \times 10^5$ <sup>b</sup>	99.116
p-Value	<0.001	0.004	<0.001	

Abbreviations: Ch, chitosan; NBG, bioactive glass nanoparticles; NHAP, nanohydroxyapatite; SD, standard deviation. Means with different letters were statically significant.

**Table 4** Mean  $\pm$  SD and p-values of viability test (MTT assay)

	(OM-PC)	(NHAP 10 µg/mL)	NHAP/chitosan (10 µg/mL)	NBG (500 µg/mL)	(DMEM-NC)
Mean $\pm$ SD	$0.930 \pm 0.042$ <sup>b</sup>	$1.502 \pm 0.243$ <sup>a</sup>	$1.645 \pm 0.23$ <sup>a</sup>	$1.551 \pm 0.292$ <sup>a</sup>	$0.821 \pm 0.019$ <sup>b</sup>
p-Value	<0.001				

Abbreviations: NBG, bioactive glass nanoparticles; NHAP, nanohydroxyapatite; SD, standard deviation. Means with different letters were statically significant.

SCAP. This might be because of the chitosan coating that directly stimulates progenitor cell differentiation at the mRNA level of ALP enzyme.<sup>40–42</sup> This superiority of the composite group comes in full agreement with Kong et al<sup>37</sup> who attributed this to the topography and quantity. Also, this finding is similar to that obtained by Ge et al<sup>39</sup> on periodontal ligament stem cells explained on basis of surface chemistry and geometry. Similar results were also obtained by Tondnevis et al<sup>43</sup> on dental pulp stem cells.

BG showed significant effect on SCAP viability and osteogenic differentiation compared to the negative control group. This is consistent with Wang et al<sup>44</sup> who tested BG on bone marrow stem cells. This could be simply explained by the increased ion release, specifically calcium ions that attracts different cells.

The nanohydroxyapatite group also showed significant effect on SCAP viability and osteogenic differentiation in compared to the negative control group. This finding is in agreement with Yang et al<sup>25</sup> who tested it on mesenchymal stem cells. This could be explained on the basis of the nanoparticle size that greatly affects its behavior in addition to the increased calcium ions release that increases cell mineralization.

Nanohydroxyapatite coated by chitosan, nanobioactive glass and nanohydroxyapatite as biomaterials, proved to enhance the osteogenic differentiation and proliferation of SCAP. This could improve the regenerative procedure in endodontic as osteogenic differentiation enhances lesion healing and laying down hard tissue structure that might be dentin like.

## Conclusion

Within the limitations of this *in vitro* study, it can be concluded that isolation of SCAP can be done from extracted fully impacted immature third molars. All tested biomaterials have the ability to induce osteogenic differentiation and proliferation of SCAP. Chitosan-coated nanohydroxyapatite biomaterial has increased ability for differentiation of SCAP to osteoblasts. Chitosan-coated nanohydroxyapatite biomaterial has increased ability for proliferation of SCAP proved by upregulated cell viability.

### Ethical Statement

The research proposal was approved by the Faculty of Dentistry Ain Shams University ethical committee with approval number FDASU-Rec IM112105.

### Conflict of Interest

None declared.

## References

- 1 Yan M, Wu J, Yu Y, et al. Mineral trioxide aggregate promotes the odonto/osteogenic differentiation and dentinogenesis of stem cells from apical papilla via nuclear factor kappa B signaling pathway. *J Endod* 2014;40(05):640–647
- 2 Sonoyama W, Liu Y, Yamaza T, et al. Characterization of the apical papilla and its residing stem cells from human immature permanent teeth: a pilot study. *J Endod* 2008;34(02):166–171
- 3 Nada OA, El Backly RM. Stem cells from the apical papilla (SCAP) as a tool for endogenous tissue regeneration. *Front Bioeng Biotechnol* 2018;6(July):103
- 4 Sun JY, Yang YS, Zhong J, Greenspan DC. The effect of the ionic products of bioglass dissolution on human osteoblasts growth cycle in vitro. *J Tissue Eng Regen Med* 2007;1(04):281–286
- 5 Xynos ID, Hukkanen MV, Batten JJ, Buttery LD, Hench LL, Polak JM. Bioglass 45S5 stimulates osteoblast turnover and enhances bone formation *In vitro*: implications and applications for bone tissue engineering. *Calcif Tissue Int* 2000;67(04):321–329
- 6 Mačković M, Hoppe A, Detsch R, et al. Bioactive glass (type 45S5) nanoparticles: in vitro reactivity on nanoscale and biocompatibility. *J Nanopart Res* 2012;14:966
- 7 El-Gendy R, Yang XB, Newby PJ, Boccaccini AR, Kirkham J. Osteogenic differentiation of human dental pulp stromal cells on 45S5 Bioglass® based scaffolds in vitro and in vivo. *Tissue Eng Part A* 2013;19(5-6):707–715
- 8 Yousefi AM, Oudadesse H, Akbarzadeh R, Wers E, Lucas-Girot A. Physical and biological characteristics of nanohydroxyapatite and bioactive glasses used for bone tissue engineering. *Nanotechnol Rev* 2014;3(06):527–552
- 9 Ratih DN, Mulyawati E, Santi RK, Kristanti Y. Antibacterial and cytotoxicity of root canal sealer with the addition of chitosan nanoparticle at various concentrations. *Eur J Dent* 2023;17(02):398–402
- 10 Putranto AW, Suprastiwi E, Meidyawati R, Agusnar H. Characterization of novel cement-based carboxymethyl chitosan/amorphous calcium phosphate. *Eur J Dent* 2022;16(04):809–814
- 11 Torres-Rosas R, Torres-Gómez N, Moreno-Rodríguez A, García-Contreras R, Argueta-Figueroa L. Anti-inflammatory and antibacterial activity of the chitosan/chlorhexidine gel commercial preparation for postexodontia treatment: an in vitro study. *Eur J Dent* 2020;14(03):397–403
- 12 Boudemagh D, Venturini P, Fleutot S, Cleymand F. Elaboration of Hydroxyapatite Nanoparticles and Chitosan/Hydroxyapatite Composites: A Present Status [Internet]. Vol. 76, *Polymer Bulletin*. Berlin: Springer; 2019:2621–2653 p.
- 13 Vafa E, Bazargan-Lari R, Bahrololoom ME. Synthesis of 45S5 bioactive glass-ceramic using the sol-gel method, catalyzed by low concentration acetic acid extracted from homemade vinegar. *J Mater Res Technol* 2021;10:1427–1436
- 14 Cengiz B, Gokce Y, Yildiz N, Aktas Z, Calimli A. Synthesis and characterization of hydroxyapatite nanoparticles. *Colloids Surf A Physicochem Eng Asp* 2008;322(1–3):29–33
- 15 Nikpour MR, Rabiee SM, Jahanshahi M. Synthesis and characterization of hydroxyapatite/chitosan nanocomposite materials for medical engineering applications. *Compos, Part B Eng* 2012;43(04):1881–1886
- 16 Vuong Bui X. Bioactive ceramic powder prepared using a new sol-gel process. *Process Appl Ceram* 2017;11(02):87–92
- 17 El shahat S, Elgendy AA, Elsewify T. Characterization of human stem cells of the apical papilla. *Ain Shams Dental Journal* 2021; 24:17–23
- 18 Chueh LH, Ho YC, Kuo TC, Lai WH, Chen YHM, Chiang CP. Regenerative endodontic treatment for necrotic immature permanent teeth. *J Endod* 2009;35(02):160–164
- 19 Miller AA, Takimoto K, Wealleans J, Diogenes A. Effect of 3 bioceramic materials on stem cells of the apical papilla proliferation and differentiation using a dentin disk model. *J Endod* 2018; 44(04):599–603
- 20 Lei G, Yan M, Wang Z, et al. Dentinogenic capacity: immature root papilla stem cells versus mature root pulp stem cells. *Biol Cell* 2011;103(04):185–196
- 21 Li J, Yan M, Wang Z, et al. Effects of canonical NF-κB signaling pathway on the proliferation and odonto/osteogenic differentiation of human stem cells from apical papilla. *Biomed Res Int* 2014;2014:319651

- 22 Gong W, Huang Z, Dong Y, et al. Ionic extraction of a novel nano-sized bioactive glass enhances differentiation and mineralization of human dental pulp cells. *J Endod* 2014;40(01):83–88
- 23 Gough JE, Jones JR, Hench LL. Nodule formation and mineralisation of human primary osteoblasts cultured on a porous bioactive glass scaffold. *Biomaterials* 2004;25(11):2039–2046
- 24 Gholami S, Labbaf S, Hourah AB, Ting HK, Jones JR, Nasr Esfahani MH. Long term effects of bioactive glass particulates on dental pulp stem cells in vitro. *Biomed Glas* 2017;3(01):96–103
- 25 Yang X, Li Y, Liu X, Zhang R, Feng Q. In vitro uptake of hydroxyapatite nanoparticles and their effect on osteogenic differentiation of human mesenchymal stem cells. *Stem Cells Int* 2018;2018:2036176
- 26 Hourah AB, Labbaf S, Ting HK, Ejeian F, Jones JR, Esfahani MHN. Influence of calcium and phosphorus release from bioactive glasses on viability and differentiation of dental pulp stem cells. *J Mater Sci* 2017;52(15):8928–8941
- 27 Amir LR, Suniarti DF, Utami S, Abbas B. Chitosan as a potential osteogenic factor compared with dexamethasone in cultured macaque dental pulp stromal cells. *Cell Tissue Res* 2014;358(02):407–415
- 28 Piccinini F, Tesesi A, Arienti C, Bevilacqua A. Cell counting and viability assessment of 2D and 3D cell cultures: expected reliability of the trypan blue assay. *Biol Proced Online* 2017;19(01):8
- 29 Di Nardo P, et al. *Adult Stem Cells Methods and Protocols*. New York, NY: Springer Science + Business Media LLC; 2017:194
- 30 Plumb JA. *Cell Sensitivity Assays: The MTT Assay*. Langdon S.P. (eds), *Cancer Cell Culture. Methods in Molecular Medicine*. Totowa, NJ: Humana Press; 2004
- 31 Gomes-Cornélio AL, Rodrigues EM, Salles LP, et al. Bioactivity of MTA Plus, Biodentine and an experimental calcium silicate-based cement on human osteoblast-like cells. *Int Endod J* 2017;50;(01):39–47
- 32 Reilly GC, Radin S, Chen AT, Ducheyne P. Differential alkaline phosphatase responses of rat and human bone marrow derived mesenchymal stem cells to 45S5 bioactive glass. *Biomaterials* 2007;28(28):4091–4097
- 33 Ryu W-S. Diagnosis and methods. *Mol Virol Hum Pathog Viruses* 2017;47–62
- 34 Magri AMP, Fernandes KR, Ueno FR, et al. Osteoconductive properties of two different bioactive glass forms (powder and fiber) combined with collagen. *Appl Surf Sci* 2017;423:557–565
- 35 Gabbai-Armelin PR, Souza MT, Kido HW, et al. Effect of a new bioactive fibrous glassy scaffold on bone repair. *J Mater Sci Mater Med* 2015;26(05):177
- 36 Kang J, Fan W, Deng Q, He H, Huang F. Stem cells from the apical papilla: a promising source for stem cell-based therapy. *BioMed Res Int* 2019;2019:6104738
- 37 Kong L, Gao Y, Lu G, Gong Y, Zhao N, Zhang X. A study on the bioactivity of chitosan/nano-hydroxyapatite composite scaffolds for bone tissue engineering. *Eur Polym J* 2006;42(12):3171–3179
- 38 Hosseinzade M, Soflou RK, Valian A, Nojehdehian H. Physico-chemical properties of MTA, CEM, hydroxyapatite and nano hydroxyapatite-chitosan dental cements. *Biomed Res* 2016;27(02):442–448
- 39 Ge S, Zhao N, Wang L, et al. Bone repair by periodontal ligament stem cellseeded nanohydroxyapatite-chitosan scaffold. *Int J Nanomedicine* 2012;7:5405–5414
- 40 Matsunaga T, Yanagiguchi K, Yamada S, Ohara N, Ikeda T, Hayashi Y. Chitosan monomer promotes tissue regeneration on dental pulp wounds. *J Biomed Mater Res A* 2006;76(04):711–720
- 41 Dash M, Chiellini F, Ottenbrite RM, Chiellini E. Chitosan - a versatile semi-synthetic polymer in biomedical applications. *Prog Polym Sci* 2011;36(08):981–1014
- 42 Lieder R. Chitosan and chitosan derivatives in tissue engineering and stem cell biology. PhD thesis, Reykjavik Univ. 2013; (January):141
- 43 Tondnevis F, Ketabi M, Fekrazad R, Sadeghi A, Abolhasani MM. Using chitosan besides nano hydroxyapatite and fluorohydroxyapatite boost dental pulp stem cell proliferation. *J Biomim Biomater Biomed Eng* 2019;42:39–50
- 44 Wang S, Huang G, Dong Y. Directional migration and odontogenic differentiation of bone marrow stem cells induced by dentin coated with nanobioactive glass. *J Endod* 2020;46(02):216–223